

# SYNTHETIC ESTERS:

Engineered to Perform

By TyleTr Housel, CLS



**ZSCHIMMER & SCHWARZ**

Chemistry tailor-made

# SYNTHETIC ESTERS:

## Engineered to Perform

- ▶ Structure and Application Properties
  - ▶ The Ester Reaction
  - ▶ Thermo-oxidative Stability
  - ▶ Viscosity
  - ▶ Biodegradability and Hydrolytic Stability
  - ▶ Smoke Point, Flash Point, Fire Point and Volatility
  - ▶ Volatility and Deposits
  - ▶ Lubricity, Polarity and Additives
- ▶ Manufacturing, Chemical Stability and Application Suitability
  - ▶ Residual Acid Value
  - ▶ Catalyst Residue
- ▶ Summary



The lubricant industry generally treats synthetic esters as a monolithic or at best bilithic class of Group V base oils with well defined properties. It is not difficult to find a chart that lists esters as having “fair” hydrolytic stability, “good” biodegradability, “very good” lubricity, “excellent” oxidative stability and so on. Sometimes diesters and polyol esters are listed separately, but there is seldom further differentiation. However, the nature of esters defies such oversimplification. There are an endless variety of esters that can be built from commonly available acids and alcohols, so almost anything is possible.

Modern synthetic esters can be ‘tuned’ to perform in nearly any environment and application. Do you need excellent hydrolytic stability? Esters can do that! How about oxidative stability? No problem! Biodegradability? Lubricity? High viscosity index? Low temperature properties? All of these are possible with the right synthetic ester. Synthetic esters are manufactured from carboxylic acids and alcohols which are very common chemical


building blocks. They provide almost unlimited structural and performance possibilities by choosing the starting materials wisely.

This white paper investigates the ways in which composition and structure determine properties and application suitability. We will also discuss the importance of the manufacturing process in producing esters that achieve the desired characteristics and retain them over time. Choosing — or creating — the right ester for an application takes expertise and experience.

## Structure and Application Properties

### The Ester Reaction

Figure 1 shows the basic chemical reaction used to synthesize all esters: a carboxylic acid and an alcohol react to form an ester and water. Organic chemists call this a reversible reaction because water can react with ester groups and break the ester into its components. This is known as hydrolysis.

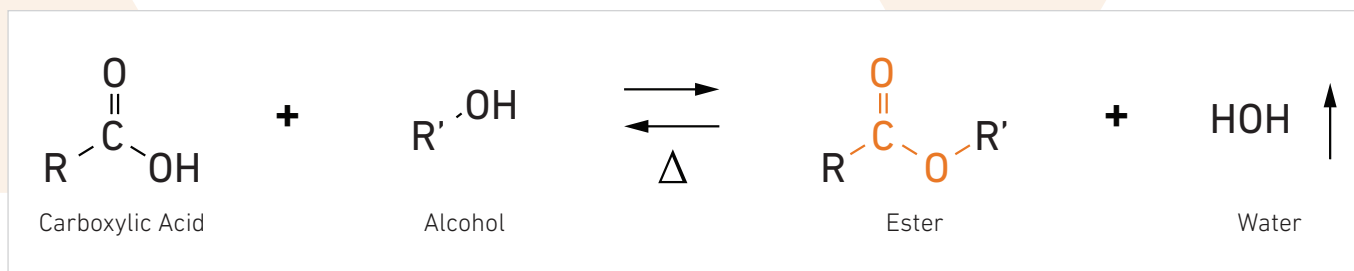

**Figure 1. The esterification reaction**

The raw materials used to make esters can be linear, branched, saturated, unsaturated, monofunctional, difunctional, or polyfunctional. There are hundreds of potential acid and alcohol building blocks, and the number of combinations is practically limitless. Attempts to classify esters in categories such as diesters and polyol esters, simple and complex esters, the technology is far ahead of the terminology and you know sometimes words have two meanings.

The building blocks often define the maximum performance potential of an ester while the manufacturing savvy determines whether the ester reaches its potential. For example, a synthetic

neopolyol (alcohol) can produce an ester with outstanding oxidative stability, but the oxidative stability of the ester may be diminished with inferior ingredients, contaminants or poor processing techniques.

### Thermo-oxidative Stability

Oxidation is a degradation process that occurs when atmospheric oxygen reacts with organic molecules. For synthetic esters, this normally occurs at high temperatures, but it is possible to find esters that oxidize without heating. People have known for centuries that linseed oil form a solid coating when exposed to air at ambient temperatures. These are called


drying oils because they can be painted on wood and cure to a hard, protective varnish. Room temperature polymerization relies on oxidative crosslinking of polyunsaturated fatty acids.

While varnish enhances the appearance of antique furniture, it is not beneficial on industrial equipment. Synthetic esters are the best choice to provide clean, varnish-free lubrication at temperatures up to 600°F/300°C. The only way to engineer a superior high temperature lubricant is to understand and eliminate structures that are oxidatively unstable. We have already seen that polyunsaturated fatty acid components must be eliminated, but unsaturated fatty acids such as oleates are commonly used in lubricants. In fact, oleates have many good properties including lubricity, low volatility, cold flow, biodegradability, renewability and are inexpensive. The oxidative stability is much better than the drying oils, but unsaturated

esters including vegetable oils are still limited to lower temperature applications.

Saturated esters are required for use at higher temperature, but there is more to the story. High temperature oxidative stability depends heavily on the number and configuration of hydrogens on the  $\beta$ -carbons in the molecule. The  $\beta$  carbon is the second one from the C-O bond of the ester group.

The  $\beta$ -hydrogen is very reactive toward oxygen, so esters with no  $\beta$ -hydrogen are more thermally stable. These are known as neopolyol esters where the name comes from their structural similarity to neopentane. Neopolyol is shortened to polyol esters and is then abbreviated to POE (apparently NPE was already taken by nonyl phenol ethoxylates). All POEs have good oxidative stability because they have no  $\beta$ -hydrogens (Figure 2).

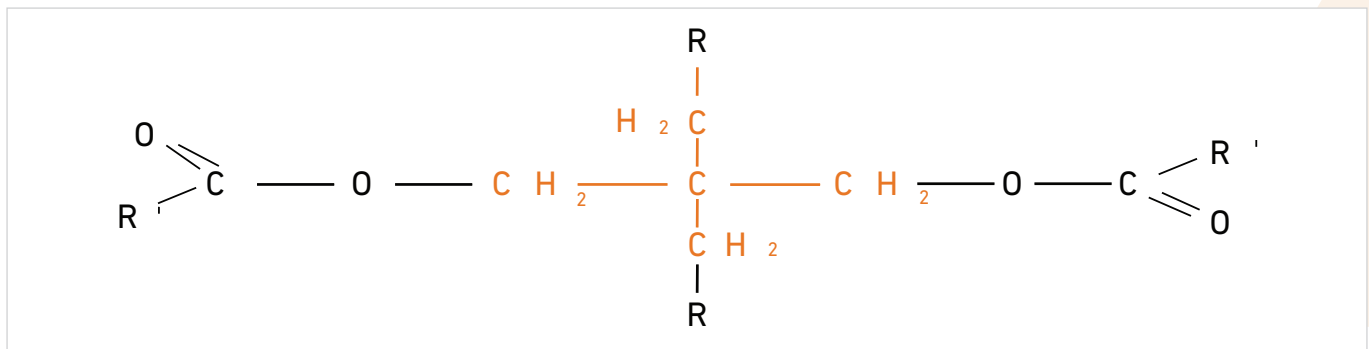

**Figure 2. Polyol ester.**

We have seen that unsaturated fatty acids cannot perform at high temperature, but in truth, it is not enough to simply substitute saturated fatty acids such as stearic acid.

Synthetic short chain carboxylic acids offer a further degree of oxidative stability and are also much better at low temperature than saturated fatty acids. Shorter branched fatty acids are used when exceptional thermal stability is required.

By eliminating the oxidative weak points, synthetic esters can be designed to operate at high temperatures and will actually tend to evaporate cleanly before undergoing oxidative polymerization so they will not form deposits and varnish.

## Viscosity

Chemists find many examples of the link between viscosity and molecular weight. From linear alkanes to polymers, we expect bigger molecules to be more viscous. However, this simple rule of thumb does not always apply to synthetic esters. The viscosity is strongly dependent on the amount of branching, aromaticity, functionality and ease of rotation of the bonds that make up the molecule. As the structure becomes more branched, it is more difficult for the molecule to bend around and flow over itself. Aromatic esters are extremely viscous because of the rigid aromatic ring. So while it's true that molecular weight is related to viscosity, there are also ways to break this

relationship when desired. This is particularly useful when the volatility profile requires a specific molecular weight and the application demands a certain viscosity.

Molecular weight is not the only factor that determines the viscosity of a synthetic ester, but it can certainly be used to increase viscosity when necessary. If the component acids and alcohols each have more than one reactive group, esters can be polymerized to any length. The lubricant industry doesn't use rigid polyesters that are made into bottles, but the same principle can be used to build molecular weight therefore increase viscosity. These are called complex esters, or CPE.

### Biodegradability and Hydrolytic Stability

The rate of the hydrolysis reaction is highly dependent on both the chemistry of the ester bond and also the environmental conditions. Synthetic ester can be stable for a few hours or thousands of years so it is impossible to classify them using words such as "fair" or "good". To manage hydrolysis, it is important to understand the type and the purity of reactants, as well as the manufacturing.

Recall that esters are made from alcohols and carboxylic acids, and that water is a byproduct of the esterification reaction. All ester reactions are reversible so that water can break the ester back into the acid and alcohol components. Hydrolytic stability is the ability of an ester to resist breakdown in the presence of water. Biodegradability is more formally defined by test protocols such as the OECD 301b test which is used to decide if chemicals are "inherently" or "readily" biodegradable. Hydrolytic stability and biodegradability are discussed together because hydrolysis is the first step toward ester biodegradation. Once the ester is broken into the alcohols and acids, bacteria can complete the digestion of the components. Typically, increasing the amount of natural components such as vegetable based fatty acids helps biodegradability. When synthetic acids and neopolyol alcohols are used, the ester becomes more inert and the rate of biodegradation is reduced.

It is possible to chemically block the hydrolysis pathway using branched carboxylic acids. These esters are extremely stable in water and act like mineral oils in typical hydrolysis tests. In fact, a computer simulation shows that the rate of hydrolytic degradation is measured in the hundreds of years.

### Smoke Point, Flash Point, Fire Point and Volatility

Synthetic esters are prized for their ability to lubricate at high temperatures. A main reason is that they have a much lower volatility than other lubricant base oils at a given viscosity. Volatility is strongly related to smoke point, flash point, and fire point which are part of ASTM D-92. As temperature increases, the amount of evaporation increases until there is visible smoke and eventually enough smoke to support a flash or fire in the presence of a flame. The table below shows the relationship between flash point and viscosity for several common types of synthetic lubricant.

SYNTHETIC BASE OIL	VISCOSITY AT 40C	FLASH POINT
PAO	19 cSt	220°C
PAG	34 cSt	218°C
Alkylated Naphthalene	29 cSt	222°C
Diester	14 cSt	231°C
Polyol ester (POE)	19 cSt	257°C

Volatility is also dependent on the distribution of molecular weights in a lubricant. We know that a small amount of flammable solvent will still be flammable even if mixed with other inert components. The mixture will ignite as long as there are enough flammable vapors in the air. By the same logic, the most volatile components of a lubricant base oil determine flash point. Esters can be designed to have a very pure, monodisperse composition so there are few small molecules to smoke and flash. An added benefit is that viscosity stays in grade because there are no light ends to evaporate from the lubricant.

### Volatility and Deposits

From a chemical standpoint, volatility is related to molecular weight, polarity and chemical stability. The first two are well known affects, but freshman chemistry normally ignores chemical stability because it considers only small organic molecules. However, a high temperature lubricant is made from larger molecules that do not evaporate readily and so stability becomes important.

Oxidative and thermal degradation begin to occur between 200°C and 300°C. At this temperature, base oil evaporation is a

slow process. However, oxidation can break the molecule into small, volatile fractions. A large percentage of the weight loss in evaporation tests such as ASTM D-2595 comes from oxidation. Not only does oxidation cause weight loss, it also causes varnish. The decomposition products in the vapor phase are often free radicals or reactive molecules. Deposits and varnish can form as the radical groups in the vapor condense and form a polymer varnish on metal surfaces. These polymers can also form sludge if they reach a high enough concentration to be insoluble in the bulk oil.

Synthetic esters reduce varnish and other deposits because they have outstanding oxidative stability and do not form many radical decomposition products. Further, they are good high temperature solvents so they tend to dissolve the varnish back into the liquid phase so it can be filtered out.

## Lubricity, Polarity and Additives

The key property of a lubricant is that it is expected to lubricate. Lubricity has to do with how easily the molecule flows over itself and how well it competes for and coats the metal surface. Esters are generally considered good boundary lubricants because they associate with metal surfaces and reduce the amount of metal-to-metal contact during sliding motion. Structural factors that impact lubricity include the chain length, the amount of branching, and the location of linkages within the molecule.

Longer carbon chains, less branching and good polarity all favor boundary lubrication. Ester linkages are polar but can be less surface active if they are shielded by carbon chains. Synthetic esters are designed from different acid and alcohol feedstocks, so the location of ester groups and type of carbon chains can be selected independently.

The lubricity of the ester basestock depends on the interaction of the ester with the metal surface. Esters have good lubricity, but under severe conditions, antiwear and extreme pressure additives are used to carry the bulk of the load.

Some say that esters compete so vigorously for the metal surfaces they crowd out additives that may be necessary. However, many additives are active enough to displace an ester

from a surface. Expertise and experience is important here, as some additives do not work well with synthetic esters. It is also important to choose an ester that is appropriate for the application. If the application involves boundary lubrication where metal surfaces grind together under pressure, lubricity is a key concern.

But if the application involves only hydrodynamic lubrication where there's no metal-to-metal contact, lubricity is less important. Esters are great for high-temperature hydrodynamic applications because they can survive in extreme environments where no other lubricant can.

## Manufacturing, Chemical Stability and Application Suitability

To this point we have discussed the role that chemical structure plays in ester properties. There is a second factor, equally important: the manufacturing process and the residuals it may leave behind.


### Residual acid value

Ester manufacturing always starts with an acid and an alcohol, both of which may be volatile. It is impossible to achieve 100% conversion in any chemical reaction so there is always some residual carboxylic acid or alcohol in the final product.

If this is not properly controlled, it can alter the initial properties of the ester, and can also cause the lubricant's properties to change during storage and use.

Carboxylic acids are the biggest concern because they can accelerate hydrolytic breakdown of the lubricant. This is a particular problem in metalworking fluids where water is a main component.

Figure 3 shows the effect of residual acid on hydrolytic stability. This is an accelerated hydrolysis test that holds an ester and water in a sealed tube at 125°C. Ester 1 (blue) has a total acid number (TAN) of 0.03 mgKOH/g, and over the duration of the test shows almost no degradation. Ester 2 (green) starts with a TAN of 1 and Ester 3 (red) starts with a TAN of 3. Esters 2 and 3 are highly degraded by the end of the test.

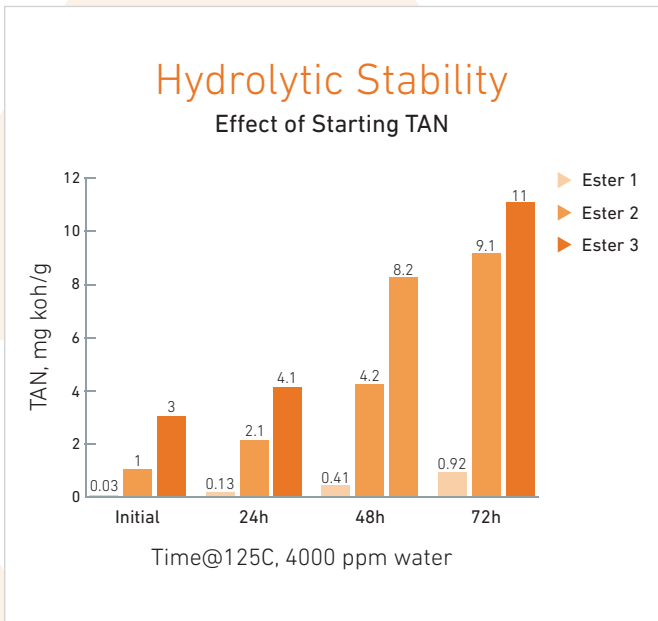


**Figure 3. Residual acid left after manufacturing shortens ester life dramatically.**

### Catalyst residue

Esters are usually made with a catalyst to accelerate the synthesis, but ester catalysts also accelerate the degradation of ester in the presence of water. It is essential to remove or deactivate the ester catalyst at the end of the manufacturing process to ensure that the ester will maintain its quality during storage, formulation and use. Further, mineral acids and certain active metals must be avoided because they can break down

any type of ester. Most ester lubricants are not recommended for applications where they will come in contact with strong acids and bases.

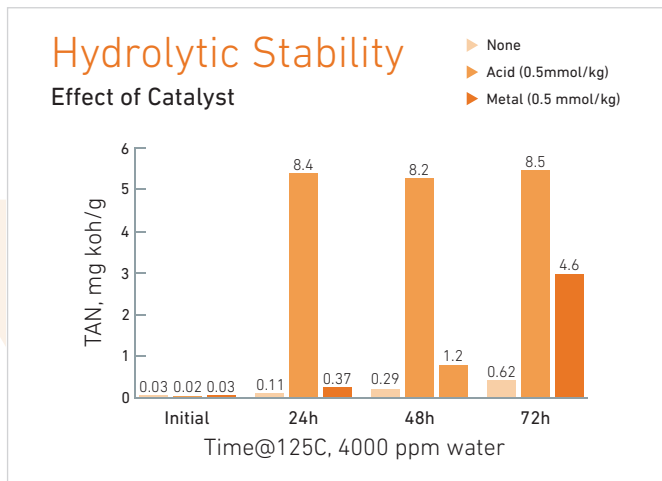

**Figure 4. Residual catalyst dramatically reduces hydrolytic stability.**

Figure 4 shows the effect of mineral acids and metals on hydrolytic stability: the three samples all start with virtually no acid present (initial TAN.02-.03 mgKOH/g). One sample (green) was treated with a mineral acid, and metal fines were added to another (red). As shown, the strong mineral acid completely hydrolyzed the sample within 24 hours. Metal fines were not as fast but had the same effect, while the untreated sample (blue) retains its integrity.

## Summary

This white paper has, we hope, made several things clearer:

- ▶ Esters are tunable for nearly any application and operating environment. They provide flexibility that almost no other chemistry can offer. It is not appropriate to generalize esters into one or two categories because the chemistry lends itself to designed performance.
- ▶ Esters are very good for extreme environments. They can be made to stand up to nearly any temperature or hydrolytic challenges.
- ▶ Esters manufacturing is important. Residual catalysts, incomplete reaction, poor raw material selection and

contamination can quickly compromise the excellent properties of a synthetic ester.

Finally, it's a good idea to consider the expertise and experience of your ester supplier. Esters can be designed and manufactured to work in almost any environment, but this means the selection process is critical. Work with someone who knows the science and technology of esters and is willing to take the time to understand your requirements. This is the only way to ensure you are getting the right product that is best for your lubrication need. The answer may not be on the existing product list. If your ester choices are limited, it isn't the chemistry it is the supplier. In short, work with someone who knows what they're doing — and work with someone who will work with you.



**ZSCHIMMER & SCHWARZ**

Chemistry tailor-made

► **Zschimmer & Schwarz**

Mohsdorf GmbH & Co. KG  
Chemnitztalstraße 1  
09217 Burgstädt | DE  
T +49 3724 67-0, F +49 3724 67-209  
info.zsm@zschimmer-schwarz.com  
zschimmer-schwarz.com

► **Zschimmer & Schwarz**

GmbH & Co KG  
Chemische Fabriken  
Max-Schwarz-Straße 3-5  
56112 Lahnstein | DE  
T +49 2621 12-0 | F +49 2621 12-407  
info@zschimmer-schwarz.com  
zschimmer-schwarz.com